

# Superfluid Density and Energy Gap-Function of Superconducting $\text{PrPt}_4\text{Ge}_{12}$

A. Maisuradze,<sup>1,\*</sup> M. Nicklas,<sup>2</sup> R. Gumeniuk,<sup>2</sup> C. Baines,<sup>1</sup> W. Schnelle,<sup>2</sup>  
H. Rosner,<sup>2</sup> A. Leithe-Jasper,<sup>2</sup> Yu. Grin,<sup>2</sup> and R. Khasanov<sup>1,†</sup>

<sup>1</sup>Laboratory for Muon Spin Spectroscopy, Paul Scherrer Institut, CH-5232 Villigen PSI, Switzerland

<sup>2</sup>Max-Planck-Institut für Chemische Physik fester Stoffe, Nöthnitzer Str. 40, 01187 Dresden, Germany

The filled skutterudite superconductor  $\text{PrPt}_4\text{Ge}_{12}$  was studied in muon-spin rotation ( $\mu\text{SR}$ ), specific heat, and electrical resistivity experiments. The continuous increase of the superfluid density with decreasing temperature and the dependence of the magnetic penetration depth  $\lambda$  on the magnetic field obtained by means of  $\mu\text{SR}$ , as well as the observation of a  $T^3$  dependence of the electronic specific heat establish the presence of point-like nodes in the superconducting energy gap. The energy gap was found to be well described by  $\Delta = \Delta_0|\hat{k}_x \pm i\hat{k}_y|$  or  $\Delta = \Delta_0(1 - \hat{k}_y^4)$  functional forms, similar to that obtained for another skutterudite superconductor,  $\text{PrOs}_4\text{Sb}_{12}$ . The gap to  $T_c$  ratios were estimated to be  $\Delta_0/k_B T_c = 2.68(5)$  and  $2.29(5)$ , respectively.

PACS numbers: 76.75.+i, 74.70.Dd, 74.25.Ha

The filled skutterudite compounds  $RM_4Pn_{12}$  ( $R$  = rare-earth or alkaline-earth,  $M$  = Fe, Ru, Os, and  $Pn$  = P, As, Sb) have attracted much attention in the recent years. Depending on the composition they may undergo metal-insulator transitions [1], show conventional or unconventional superconductivity [2, 3, 4], become magnetic [5, 6, 7], semiconducting [8], or exhibit the Kondo effect [9] *etc.* One of the most interesting discoveries was superconducting Pr-filled skutterudites, since within the traditional mechanism of  $s$ -wave Cooper pairing the Pr magnetism would destroy superconductivity. The first compound demonstrating such unusual behavior was  $\text{PrOs}_4\text{Sb}_{12}$  [2]. The Cooper-pairing mechanism and the corresponding symmetry of the superconducting energy gap in  $\text{PrOs}_4\text{Sb}_{12}$  are still under debate. Studies of the thermal conductivity suggested the presence of two distinct superconducting phases [10]. Penetration depth experiments were pointing either to a possible nodal structure of the gap [11] or to a gap without nodes [3]. A number of experimental techniques such as scanning tunneling microscopy [12], thermal conductivity [13], and specific heat measurements [14] are in agreement with a fully developed isotropic  $s$ -wave superconducting gap.

Recently, a new Pr-containing skutterudite superconductor  $\text{PrPt}_4\text{Ge}_{12}$  was discovered [15]. Specific heat experiments reveal strongly coupled superconductivity with a transition temperature  $T_c \simeq 7.9$  K, factor of 4 higher than that in  $\text{PrOs}_4\text{Sb}_{12}$  [2], thus making  $\text{PrPt}_4\text{Ge}_{12}$  more accessible for e.g. spectroscopic studies. Here, we report on a study of  $\text{PrPt}_4\text{Ge}_{12}$  by means of muon-spin rotation ( $\mu\text{SR}$ ), specific heat, and electrical resistivity. The linear increase of the superfluid density ( $\rho_s$ ) with decreasing temperature, its dependence on the magnetic field, as well as the observation of a  $T^3$  dependence of the electronic specific heat document presence of the point-like nodes in the energy gap. The temperature dependence of  $\rho_s$  was analyzed with various gap models suggested previously for  $\text{PrOs}_4\text{Sb}_{12}$  and found to be well described by two models of axial symmetry with point-like nodes:

$$\Delta = \Delta_0|\hat{k}_x \pm i\hat{k}_y| \text{ or } \Delta = \Delta_0(1 - \hat{k}_y^4).$$

The sample preparation procedure of  $\text{PrPt}_4\text{Ge}_{12}$  is described in [15]. The transverse field (TF)  $\mu\text{SR}$  experiments were performed at the  $\pi\text{M}3$  beam line at the Paul Scherrer Institute (Villigen Switzerland). The sample was field-cooled from above  $T_c$  down to 1.5 K and measured as a function of temperature in a series of fields ranging from 35 mT to 640 mT. Additional experiments down to  $T \simeq 0.03$  K were performed at 75 mT. Typical counting statistics were  $\sim 7 \times 10^6$  positron events per each particular data point. Electrical resistivity  $R(T, H)$  and specific heat  $C(T)$  down to 0.4 K were measured in a commercial system (PPMS, Quantum Design) using an AC bridge (LR-700, Linear Research) and the HC option of the PPMS, respectively.

Figure 1 shows the electronic specific heat  $C_{\text{el}}/T$  vs  $T^2$ . The phonon contribution  $\propto T^3$  was subtracted using a Debye temperature  $\Theta_D = 189$  K. The normal state electronic term is  $\gamma_N = 63(2)$  mJ mol<sup>-1</sup> K<sup>-2</sup>. At the lowest temperatures an upturn from a nuclear Schottky contribution of Pr becomes visible ( $C_{\text{nuc}} \propto T^{-2}$ ). After its subtraction we find  $C_{\text{el}}(T) = \gamma'T + \eta T^3$  with  $\gamma' \approx 1.33$  mJ mol<sup>-1</sup> K<sup>-2</sup> originating from a minor metallic impurity phase. For  $T/T_c < 0.2$  the clear  $T^3$  dependence of the superconducting state electronic term ( $\eta = 2.93(2)$  mJ mol<sup>-1</sup> K<sup>-4</sup>) suggests that the gap function of  $\text{PrPt}_4\text{Ge}_{12}$  has point-like nodes [16]. The further detailed investigation of the energy gap and the order parameter symmetry was performed in TF  $\mu\text{SR}$  experiments.

The TF  $\mu\text{SR}$  data were analyzed as follows. The spatial magnetic field distribution within the flux line lattice (FLL) was calculated in a standard way via:

$$B(\mathbf{r}) = \langle B \rangle \sum_{\mathbf{G}} \exp(-i\mathbf{G} \cdot \mathbf{r}) B_{\mathbf{G}}(\lambda, \xi, b). \quad (1)$$

Here,  $\langle B \rangle$  is the average magnetic field inside the superconductor,  $\xi$  the coherence length,  $b = \langle B \rangle / B_{c2}$  the reduced field,  $\mathbf{r}$  the vector coordinate in a plane perpendicular

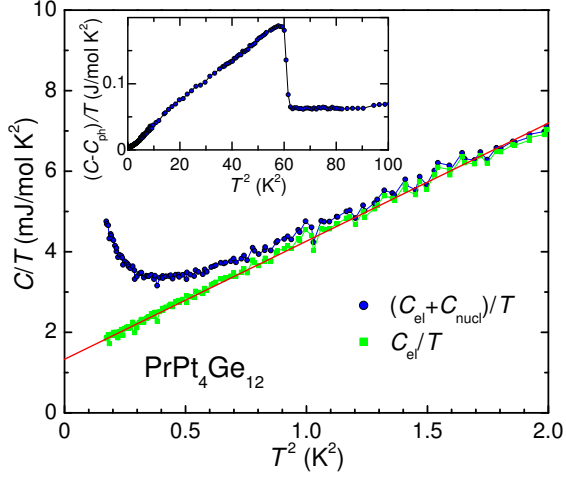


FIG. 1: (Color online) Inset: specific heat  $C - C_{ph}$  of  $\text{PrPt}_4\text{Ge}_{12}$  corrected for the phonon term. Main panel: data below 1.4 K and data corrected for the nuclear Schottky contribution of Pr (see text).

ular to the applied field,  $\mathbf{G} = 4\pi/\sqrt{3}a(m\sqrt{3}/2, n+m/2)$  the reciprocal lattice vector of the hexagonal FLL,  $a$  the intervortex distance, and  $m$  and  $n$  are integer numbers. The Fourier components  $B_{\mathbf{G}}$  were obtained by minimizing the Ginzburg-Landau (GL) free energy using the numerical algorithm described in Ref. 17. The  $\mu\text{SR}$  time-spectra were fit to a theoretical polarization function  $\tilde{P}(t)$  by assuming the internal field distribution  $P_{\text{id}}(B)$  obtained from Eq. (1) and accounting for the FLL disorder by multiplying  $P_{\text{id}}(B)$  to a Gaussian function [18]:

$$\tilde{P}(t) = Ae^{i\phi} \int e^{-(\sigma_g^2 + \sigma_{nm}^2)t^2/2} P_{\text{id}}(B) e^{i\gamma_\mu Bt} dB. \quad (2)$$

Here  $A$  and  $\phi$  are the initial asymmetry and the phase of the muon spin ensemble,  $\sigma_g$  is a parameter related to FLL disorder [19] and  $\sigma_{nm}$  the nuclear moment contribution measured at  $T > T_c$ . For a detailed description of the fitting procedure we refer to [20].

Figure 2 shows representative internal field distributions  $P(B)$  obtained from the measured  $\mu\text{SR}$  time-spectra by performing the fast Fourier transform. The solid lines correspond to the fits by means of the above described procedure.  $P(B)$ 's have asymmetric shape as expected for a field distribution within well arranged FLL. The small peak in the vicinity of the applied field is due to muons stopped outside of the sample ( $\sim 2\text{-}3\%$ ). Above  $T_c$  an additional magnetic depolarization is observed, which increases with increasing field. The measurements at zero field and above  $T_c$  revealed that this magnetic depolarization is temperature independent.

Magnetic penetration depth is defined in the London limit of low magnetic fields as a measure of superfluid density  $\rho_s \propto 1/\lambda^2$ . The  $\lambda$  obtained in the vortex state is often called an effective magnetic penetration depth  $\lambda_{\text{eff}}$  [21, 22], since it might be field dependent. For a classical

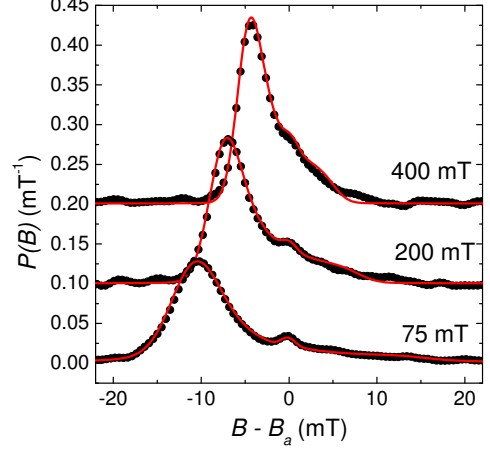


FIG. 2: (Color online) The magnetic field distribution  $P(B)$  at  $T = 1.55$  K and applied fields  $B_a = 75, 200$ , and  $400$  mT obtained by means of fast Fourier transform. The solid lines are fits to the data (see text for details).

BCS superconductor with isotropic s-wave gap  $\lambda_{\text{eff}} = \lambda$  [22]. The fit of Eq. (2) to the single  $\mu\text{SR}$  time-spectra does not allow to obtain independently  $\lambda$  and  $\xi$ , since they strongly correlate [20]. In order to get rid of this correlation one needs to perform a *simultaneous* fit of several spectra, measured at the same temperature but different magnetic fields, with  $\lambda$  and  $\xi$  as common parameters [19, 20].  $B_{c2} = \Phi_0/2\pi\xi^2$  as a function of temperature, obtained after such fit, is presented in Fig. 3a. The fit was performed by combining the data points measured at the applied fields  $B_a = 35$  and  $400$  mT. Figures 3b and c show the corresponding correlation plots  $[\chi^2(\lambda, \xi)]$ . The normalized  $\chi^2$  was obtained for  $\lambda$  and  $\xi$  varied within 10% around their optimal fit values [ $\lambda_0 = 114(4)$  nm and  $\xi_0 = 18.1(8)$  nm]. Strong correlations between  $\lambda$  and  $\xi$  as well as a field dependent slope of the correlation curves are obvious. Figure 3a implies, however, that  $B_{c2}(T)$  obtained in the simultaneous fit is approximately 40% smaller than that measured directly in specific heat [15] and resistivity experiments. This suggests that the assumption of field-independent  $\lambda$  may not be valid for  $\text{PrPt}_4\text{Ge}_{12}$  and  $\lambda$  depends on field. Field dependence of  $\lambda$  is expected for a superconductor with nodes in the gap. A field induces excitations at the gap nodes due to nonlocal and nonlinear effects, thus reducing superconducting carrier concentration  $n_s \propto 1/\lambda^2$  [21]. We believe however that GL theory developed for superconductors with isotropic s-wave gap is approximately valid in the present case. In order to avoid the correlation between  $\lambda$  and  $\xi$  we fixed the values of  $\xi(T) = \sqrt{\Phi_0/2\pi B_{c2}(T)}$  by using the  $B_{c2}(T)$  curve obtained in resistivity measurements (see Fig. 3a) [15].

The GL theory allows to extend the London definition of superfluid density for a finite applied field [23]:

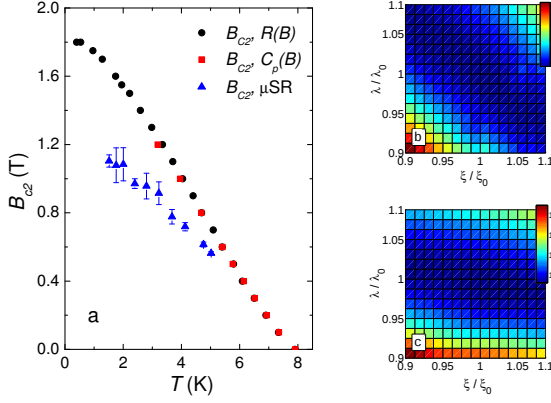


FIG. 3: (Color online) (a) Temperature dependence of the upper critical field  $B_{c2}$  obtained in specific heat (squares) and resistivity (dots) experiments compared with results of the simultaneous fit of  $\mu$ SR time spectra at 35 and 400 mT (triangles). Panels (b) and (c) show correlation plots  $\chi^2(\lambda, \xi)$  for  $B_a = 400$  mT and 50 mT, respectively.

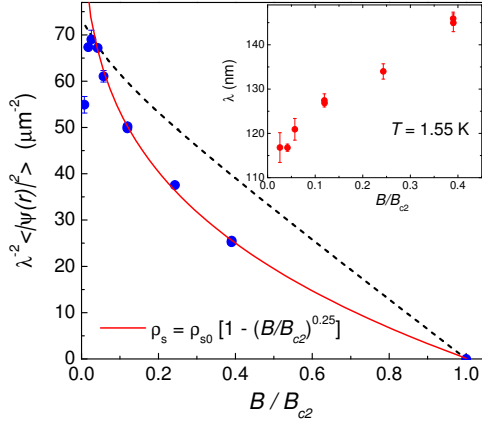


FIG. 4: (Color online) Field dependence of the superfluid density  $\rho_s \propto \langle |\psi|^2 \rangle / \lambda^2$ . The solid line is the power law fit  $\rho_s(T)/\rho_s(T=0) = 1 - (B/B_{c2})^\alpha$  with  $\alpha \simeq 0.25$ . The dashed line represents the case when  $\lambda$  does not depend on the magnetic field. The inset shows  $\lambda(B/B_{c2})$  at  $T = 1.55$  K.

$$\rho_s \propto \langle |\psi(\mathbf{r})|^2 \rangle / \lambda^2 \simeq (1 - b) / \lambda^2. \quad (3)$$

Here,  $\psi(\mathbf{r})$  is the GL order parameter and  $\langle \dots \rangle$  means averaging over the unit cell of the FLL.

Equation (3) implies that in an isotropic s-wave superconductor the mean superfluid density decreases with increasing field as  $\langle |\psi(\mathbf{r})|^2 \rangle$  (the dashed line in Fig. 4). Obviously, the experimental  $\rho_s$  decreases much stronger with increasing magnetic field than for a field-independent  $\lambda$ , thus suggesting the presence of nodes in the gap. The power law fit  $\rho_s(T)/\rho_s(T=0) = 1 - b^\alpha$  results in  $\alpha = 0.26(2)$  (solid line in Fig. 4).

Figure 5a shows  $\rho_s$ , normalized to its value at  $T = 30$  mK, as a function of the reduced temperature  $t =$

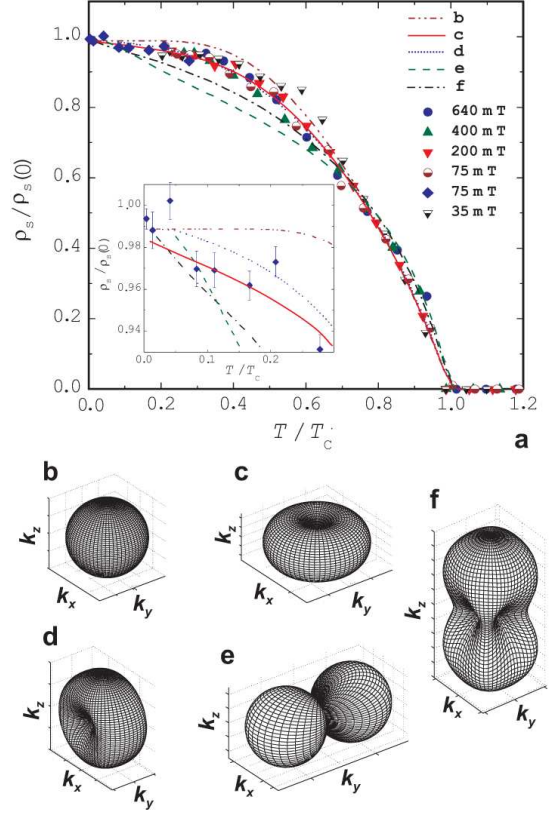


FIG. 5: (a) Temperature dependence of  $\rho_s \propto \langle |\psi(\mathbf{r})|^2 \rangle / \lambda^2$  normalized to its value at  $T = 30$  mK. The lines represent the fits by using 5 different gap models. The inset shows the low temperature region between  $T = 0$  and  $T = 0.3T_c$ . The panels from (b) to (f) represent the gap functions used for the analysis of  $\rho_s(T)$  data (see Table I for details).

$T/T_c$ . Surprisingly, the  $t$  dependence of  $\rho_s$  is identical for all applied fields. Only the data points measured at 35 mT deviate slightly. This may be due to larger vortex disorder and, consequently, enlarged systematic errors at such a low field. The inset of Fig. 5a shows  $\rho_s$  measured at 75 mT for  $T \leq 0.3T_c$ . It is obvious that  $\rho_s$  does not saturate but increases continuously with decreasing temperature as expected for a superconductor with nodes in the gap. Note that the presence of nodes is also consistent with the conclusion drawn from the analysis of  $\rho_s(b)$  (see Fig. 4 and the discussion above).

We are not aware of any work reporting the possible order parameter symmetry in  $\text{PrPt}_4\text{Ge}_{12}$ . This issue was thoroughly studied for another representative of the skutterudite family  $\text{PrOs}_4\text{Sb}_{12}$  [11, 24]. Consequently, the temperature dependence of the superfluid density was analyzed by assuming the following gap symmetries: (1) the isotropic gap  $\Delta(\theta, \phi) = \Delta_0$  (Fig. 5b), (2)  $\Delta(\theta, \phi) = \Delta_0 |\hat{k}_x \pm i\hat{k}_y| = \Delta_0 \sin \theta$  (Fig. 5c), (3)  $\Delta(\theta, \phi) = \Delta_0(1 - \hat{k}_x^4 - \hat{k}_y^4) = \Delta_0(1 - \sin^4 \theta \cos^4 \phi - \sin^4 \theta \sin^4 \phi)$  (Fig. 5d), (4)  $\Delta(\theta, \phi) = \Delta_0(1 - \hat{k}_y^4) = \Delta_0(1 - \sin^4 \theta \sin^4 \phi)$

TABLE I: Summary of the gap analysis of  $\rho_s(T)$  for PrPt<sub>4</sub>Ge<sub>12</sub> (see text for details).

| $\Delta(\phi, \theta)$                    | Panel in<br>Fig. 5 | $\Delta_0$<br>(meV) | $\Delta_0$<br>$k_B T_c$ | $\chi^2$<br>$\chi^2(\Delta_0 \hat{k}_x \pm i\hat{k}_y )$ |
|-------------------------------------------|--------------------|---------------------|-------------------------|----------------------------------------------------------|
| $\Delta_0$                                | b                  | 1.33(4)             | 1.95(5)                 | 3.79                                                     |
| $\Delta_0 \hat{k}_x \pm i\hat{k}_y $      | c                  | 1.82(4)             | 2.68(5)                 | 1                                                        |
| $\Delta_0(1 - \hat{k}_y^4)$               | d                  | 1.56(4)             | 2.29(5)                 | 1.12                                                     |
| $\Delta_0 \hat{k}_y $                     | e                  | 3.32(20)            | 4.88(30)                | 8.85                                                     |
| $\Delta_0(1 - \hat{k}_x^4 - \hat{k}_y^4)$ | f                  | 2.61(10)            | 3.84(14)                | 3.29                                                     |

(Fig. 5e), and (5)  $\Delta(\theta, \phi) = \Delta_0\hat{k}_y = \Delta_0|\sin\theta\sin\phi|$  (Fig. 5f). Here  $\Delta_0$  is the maximum value of the gap at  $T = 0$ , and  $\theta$  and  $\phi$  are the polar and the azimuthal coordinates in the  $k$ -space. The temperature dependence of the gap  $\Delta(\theta, \phi, T) = \Delta(\theta, \phi)\delta(T)$  was assumed to follow the weak-coupling BCS prediction  $\delta(T) = \tanh\{1.82[1.018(T - 1)^{0.51}]\}$  [25]. Note,  $\delta(T)$  is practically independent of gap model [26]. Although the gaps described by (2) and (3) have similar shape (see Figs. 5c and d), the  $\Delta = \Delta_0(1 - \hat{k}_y^4)$  one corresponds to triplet pairing [24] which is observed in PrOs<sub>4</sub>Sb<sub>12</sub> [4].

The temperature dependence of the superfluid density was calculated within the local (London) approximation by using the equations [26]:

$$\rho_{bb}^{aa} = 1 - \frac{3}{4\pi T} \int \sin^2\theta \left( \frac{\cos^2\phi}{\sin^2\phi} \right) \cosh^{-2} \left( \frac{\epsilon^2 + \Delta^2}{2T} \right) d\epsilon d\phi d\theta \quad (4)$$

$$\rho_{cc} = 1 - \frac{3}{2\pi T} \int \cos^2\theta \cos^2\phi \cosh^{-2} \left( \frac{\epsilon^2 + \Delta^2}{2T} \right) d\epsilon d\phi d\theta \quad (5)$$

Here,  $\rho_{ii}$  ( $i = a, b$ , or  $c$ ) is the component of the superfluid density along  $i$ th principal axis. Since our experiments were performed on a polycrystalline sample, we used the powder average of the superfluid density:

$$\rho_s = (\sqrt{\rho_{aa}\rho_{bb}} + \sqrt{\rho_{aa}\rho_{cc}} + \sqrt{\rho_{cc}\rho_{bb}})/3. \quad (6)$$

The fit was made for the only free parameter  $\Delta_0$ . The results of the fit are presented in Fig. 5a and Table I. The goodness of fit was checked by using the  $\chi^2$  criterion. The values of  $\chi^2$  normalized to that obtained for the best  $\Delta_0|\hat{k}_x \pm i\hat{k}_y|$  model are given in the last column of Table I. It is obvious that the fits using gaps of the form:  $\Delta = \Delta_0(1 - \hat{k}_x^4 - \hat{k}_y^4)$ ,  $\Delta = \Delta_0\hat{k}_y$ , and  $\Delta = \Delta_0$  are very poor. The smallest  $\chi^2$  was obtained for the  $\Delta = \Delta_0|\hat{k}_x \pm i\hat{k}_y|$  model, while the  $\Delta = \Delta_0(1 - \hat{k}_y^4)$  model results in  $\simeq 12\%$  larger  $\chi^2$  value. The gap-to- $T_c$  ratios were estimated to be  $\Delta_0/k_B T_c = 2.68(5)$  and  $2.29(5)$  for the  $\Delta_0|\hat{k}_x \pm i\hat{k}_y|$  and  $\Delta_0(1 - \hat{k}_y^4)$  gap functions, respectively. Both ratios are higher than the BCS weak coupling value 1.76, thus suggesting that PrPt<sub>4</sub>Ge<sub>12</sub> is

a moderately strong coupled superconductor. They are also relatively close to  $\Delta/k_B T_c = 2.35$  obtained from specific heat [15].

To conclude, the PrPt<sub>4</sub>Ge<sub>12</sub> skutterudite superconductor was studied in  $\mu$ SR, specific heat, and electric resistivity experiments. For  $T/T_c < 0.2$  a clear  $T^3$  dependence of the electronic specific heat term gives evidence that the gap function of PrPt<sub>4</sub>Ge<sub>12</sub> has point nodes. Analysis of the  $\mu$ SR data was performed by exact minimization of the Ginzburg-Landau free energy. The dependence of the superfluid density ( $\rho_s$ ) on the magnetic field was found to follow  $\rho_s \propto 1 - (B/B_{c2})^{0.25}$ . The temperature dependence of  $\rho_s(T)$  was found to be well described by two models with axial symmetry with point-like nodes in the gap:  $\Delta = \Delta_0|\hat{k}_x \pm i\hat{k}_y|$  and  $\Delta = \Delta_0(1 - \hat{k}_y^4)$  despite of cubic symmetry of crystal structure. The maximum gap-to- $T_c$  ratios were estimated to be  $\Delta_0/k_B T_c = 2.68(5)$  and  $2.29(5)$ , respectively, in agreement with 2.35 reported in Ref. 15 based on specific heat results.

This work was performed at the Swiss Muon Source ( $\mu$ SR), Paul Scherrer Institut (PSI, Switzerland). We would like to acknowledge E. H. Brandt for valuable discussions.

\* Electronic address: alexander.maisuradze@psi.ch

† Electronic address: rustem.khasanov@psi.ch

- [1] M. Matsunami *et al.*, Phys. Rev. B **72**, 073105 (2005).
- [2] E. D. Bauer *et al.*, Phys. Rev. B **65**, 100506(R) (2002).
- [3] D. W. MacLaughlin *et al.*, Phys. Rev. Lett. **89**, 157001 (2002).
- [4] Y. Aoki *et al.*, Phys. Rev. Lett. **91**, 067003 (2003).
- [5] G. Sheet *et al.*, Phys. Rev. B **72**, 180407(R) (2005).
- [6] T. A. Sayles *et al.*, Phys. Rev. B **77**, 144432 (2008).
- [7] W. Schnelle *et al.*, Phys. Rev. B **77**, 094421 (2008).
- [8] Y. Nakanishi *et al.*, Phys. Rev. B **75**, 134411 (2007).
- [9] H. Hidaka *et al.*, Phys. Rev. B **71**, 073102 (2005).
- [10] K. Izawa *et al.*, Phys. Rev. Lett. **90**, 117001 (2003).
- [11] E. E. M. Chia *et al.*, Phys. Rev. Lett. **91**, 247003 (2003).
- [12] H. Suderow *et al.*, Phys. Rev. B **69**, 060504(R) (2004).
- [13] G. Seyfarth *et al.*, Phys. Rev. Lett. **97**, 236403 (2006).
- [14] T. Sakakibara *et al.*, J. Phys. Soc. Jpn. **76**, 051004 (2007).
- [15] R. Gumeniuk *et al.*, Phys. Rev. Lett. **100**, 017002 (2008).
- [16] M. Sigrist and K. Ueda, Rev. Mod. Phys. **63**, 239 (1991).
- [17] E. H. Brandt, Phys. Rev. Lett. **78**, 2208 (1997).
- [18] E. H. Brandt, J. Low Temp. Phys. **26**, 709 (1977); *ibid* **73**, 355 (1988).
- [19] T. M. Riseman *et al.*, Phys. Rev. B **52**, 10569 (1995).
- [20] A. Maisuradze *et al.*, J. Phys.: Condens. Matter **21**, 075701 (2009).
- [21] M. H. S. Amin, M. Franz, and I. Affleck, Phys. Rev. Lett. **84**, 5864 (2000).
- [22] I. L. Landau and H. Keller, Physica C **466**, 131 (2007).
- [23] P. Lipavský *et al.*, Phys. Rev. B **65**, 144511 (2002).
- [24] K. Maki *et al.*, Europhys. Lett. **68**, 720 (2004).
- [25] A. Carrington and F. Manzano, Physica C **385**, 205 (2003).
- [26] R. Prozorov and R. W. Giannetta, Supercond. Sci. Technol. **19**, R41 (2006).